

## Electrochemical Reactivity of C<sub>60</sub> Modified Carbon Paste Electrode by Physical Vapor Deposition Method

S.V. Lokesh<sup>1</sup>, B.S. Sherigara<sup>1,\*</sup>, Jayadev<sup>2</sup>, H.M. Mahesh<sup>2</sup> and Ronald J. Mascarenhas<sup>3</sup>

<sup>1</sup> Department of PG Studies and Research in Industrial Chemistry, Kuvempu University, Jnana Sahyadri Shankaraghatta, Shimoga- 577 451, Karnataka, India.

<sup>2</sup> Department of PG Studies and Research in Electronics, Kuvempu University, Jnana Sahyadri, Shankaraghatta, Shimoga-577 451, Karnataka, India

<sup>3</sup> Department of Chemistry, St. Joseph's College, Bangalore, Karnataka, India.

\*E-mail: [bssherigara@rediffmail.com](mailto:bssherigara@rediffmail.com)

Received: 31 January 2008 / Accepted: 28 February 2008 / Online published: 20 March 2008

---

The electrochemical performance of vapor deposited fullerene (C<sub>60</sub>) on carbon paste electrode (CPE), by physical vapor deposition method (PVD) has been assessed. Fullerene deposited at different thickness and their voltammetric response to ferricyanide and dopamine are examined. Scanning electron microscopy was used to characterize surface morphology of C<sub>60</sub>/CPE. The cyclic voltammetric studies reveal that the electrocatalytic activity depends on thickness of the fullerene film deposited. We found that catalytic activity slightly enhances when thickness of fullerene film maintained 3 angstrom onto CPE. These differences in the electrochemical reactivity are attributed to different surface chemistry of fullerene layers. Further the modified electrode was practically applied for the simultaneous determination of adenine (A) and guanine (G). Voltammetric studies shows that guanine and adenine produced well-defined oxidation peaks at about +0.67 and +0.99 V respectively in pH 7.2 phosphate buffer.

---

**Keywords:** Fullerene, Physical Vapor Deposition, Dopamine, Adenine, Guanine

### 1. INTRODUCTION

The discovery of fullerene [1], their production [2], fullerene electrochemistry [3] and electrochemical properties of fullerene [4] triggered rapt attention and application of fullerene in the filed of electrochemistry. Fullerene and carbon nanotube electrodes have great impact on catalytic and sensor applications [5-6]. Previous studies reveal that the preparation of C<sub>60</sub> films by sublimation method [7-11] upholds the advantage over solvent evaporation method both by avoiding solvent entrapments and hopefully would be more continuous films, whereas in solvent evaporation method

films were discontinuous and contained entrapped solvent. Deposition of fullerene films from  $C_{60}$  beams produced by sublimation of  $C_{60}$  powder in high vacuum using a home made effusive oven [12] was reported.

We know that  $C_{60}$  films constitute a new class of carbon electrodes with properties that differ from graphite and diamond electrodes. These films are quite stable to oxidative potentials, but show unusual electrochemical dependence on the method of preparation and the electrolyte medium. Adlayers prepared by sublimation in vacuum reveal good uniformity even when surface mobility is low and deposition (adsorption) is fast. This has been testified by scanning probe microscopy among other analytical methods [13]

Leiro *et. Al* [9] reported the sublimation of fullerene ( $C_{60}$ ) films deposited on Si(111) surface.  $C_{60}$  films prepared by sublimation at 575 °C for 5 min on a pyrolytic carbon film electrode[11] reduction mechanism in which ion transport, the specific nature of the interaction between cation and fulleride is defined. Nanostructured fullerene films of controlled surface topography have been prepared by electrophoretic deposition [14].

Utilization of fullerene materials for the development of next generation nanodevices requires preparation of robust films on desired electrode surfaces with a well-controlled morphology. Since the properties of fullerene-containing films are profoundly controlled by the deposition conditions, substrate of adsorption, and influenced by impurities or disordered surface structures, the progress of such new fullerene-based materials strongly relies on the development of new versatile and broad preparative methodologies.

To our knowledge there is no literature regarding the physical vapor deposition of  $C_{60}$  onto carbon paste electrode. The goal of the present study is to report electrochemical reactivity and performance of carbon paste electrode modified with fullerene by physical vapor deposition (PVD) method. In the following sections we examined the influence of fullerene film onto carbon paste electrode on the electrocatalytic behavior and analytical performance of  $C_{60}$ -modified electrodes. Fullerene coating shown to influence the current response through their effect on the surface chemistry and morphology like, defect density or presence of impurities. Potassium ferricyanide and dopamine were selected as model analytes owing to their considerable importance in their accelerated electron transfer at fullerene modified electrodes. Dopamine is a neuromodulator in the brain, influencing a variety of motivated behaviors and involved in several neurologic diseases. Dopamine, which results as quasireversible system at GCE, Pt electrodes, here at  $C_{60}$ /CPE modified electrode, it acts as a reversible system, the difference in peak potential is 60 mV and current ratio is almost equal to unity was observed.

Further, we try to utilize the  $C_{60}$ /CPE modified electrode for simultaneous determination of adenine and guanine, the analysis of these bases has great significance to bioscience and clinical diagnosis. To date, some electrochemical detection protocols have been developed, such as electrochemically pretreated glassy carbon electrode [15], nafion-ruthenium oxide pyrochlore chemically modified electrode [16], highly boron-doped diamond electrode [17], and cobalt (II) phthalocyanine modified carbon paste electrode [18], b-Cyclodextrin incorporated carbon nanotubes-modified electrodes [19] etc. Now  $C_{60}$ /CPE modified electrode applied for the successful simultaneous determination of adenine and guanine.

## 2. EXPERIMENTAL PART

### 2.1. Electrochemical Apparatus and Chemicals

High purity C<sub>60</sub> (99.99%) was obtained from SES Research. Dopamine, adenine and guanine were obtained from Fluka and used without further purification. All other reagents used throughout the experiment were analytical grade. All solutions and subsequent dilutions were prepared daily, using doubly distilled water. Cyclic voltammetric measurements were conducted using a Electroanalyser model EA 201 from Chemilink Systems, Mumbai, India. The temperature of cell solution was maintained at  $25.0 \pm 0.1^{\circ}\text{C}$ . In all cases a standard three-electrode configuration was employed along with a typical cell. A fullerene modified or unmodified carbon paste electrode served as the working electrode with platinum wire as the counter electrode and an SCE reference electrode completing the cell assembly.

### 2.2. Scanning Electron Microscopy (SEM)

Micrographs of the electrode surfaces were obtained by scanning electron microscopy (SEM) using a Hitachi model S-3200N microscope.

### 2.3. Preparation of Carbon paste electrode

The carbon powder (particle size 50 mm, density 20-30g/100mL) was mixed with the binder, silicone oil, in an agate mortar and homogenized using the pestle. The electrode consisted of a teflon well, mounted at the end of a teflon tube. The prepared paste was filled into the teflon well. A copper wire fixed to a graphite rod and inserted into the Teflon tube served to establish electrical contact with the external circuit. The electrode surface of the working electrode was renewed mechanically by smoothing some paste off and then polishing on a piece of transparent paper before conducting each of the experiments. The experiments were performed in unstirred solutions.

### 2.4. Coating of the C<sub>60</sub> onto CPE

Fullerene was coated on to the tip of the electrode by physical vapor deposition method using the vacuum coating unit, model 12a 4D; Hind high vacuum company Pvt. Ltd Bangalore, India.

## 3. RESULTS AND DISCUSSION

### 3.1. Physical vapor deposition of C<sub>60</sub> Films

Fullerene was coated on to the tip of the electrode by physical vapor deposition method [7-11] using the vacuum coating. The electrode was mounted firmly on the substrate holder situated inside the


vacuum chamber. The sample electrode was kept at a distance of 4.5 cm from the source to get the uniform coating. About 1 mg of the fullerene sample was taken in the molybdenum boat. A dimple was made to the molybdenum boat to keep the sample to act as a point source. The boat was connected to the electrodes for heating. The vacuum inside the chamber was made to  $10^{-5}$  m bar (1 m bar = 0.76 Torr). When high current is applied to the molybdenum boat through the electrodes, the sample gets evaporated. The evaporation was made at the rate of  $1 \text{ \AA}/\text{sec}$ , which was controlled by applying the current. The  $C_{60}$  was coated to a desired thickness, which was monitored using a quartz crystal microbalance sensitive to mass changes of a thin metal electrode on a piezoelectric quartz crystal. Pure solid  $C_{60}$  forms a hexagonal lattice with a nearest neighbour distance close to  $10 \text{ \AA}$  [20-21].

### 3.2. Characterization of the fullerene film Layer

The fullerene film was characterized using different methodologies.

**Physical Characterization:** Sublimed fullerene films ranged in color from gold to dark brown, darkening with the sublimation time. Gold highlights on the film surface could be seen with the naked eye, indicating the film.

**Scanning electron microscopy:** The SEM images of the modified working electrode are shown in Fig.1, and compared the morphology of the immobilized layer of bare CPE and fullerene film surface on CPE. The growth process could be observed clearly by SEM.

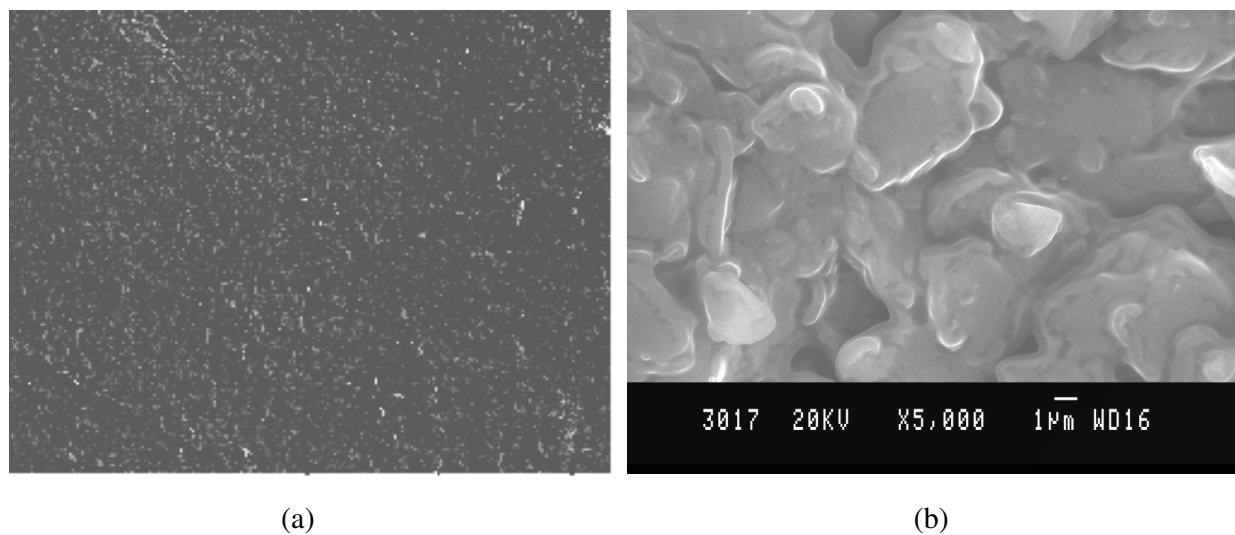

**Figure 1.** Scanning electron microscopic images of (a) bare carbon paste electrode (b)  $C_{60}$  deposited carbon paste electrode


The dispersion of fullerene film size became larger with the increasing amount of fullerene. It is seen from Fig. 1 that the carbon paste surface is covered by fullerene film. This morphology is very much different from that of original surface and the vapoured fullerene film is much smoother than the bare carbon paste surface.

### 3.3. Stability of the electrode

The modified electrode was found to be stable, even after 15 cyclic voltammetric scans. The fullerene film is quite stable, once prepared can be used for almost for about 15 days if preserved properly. We did not observe any damage to the fullerene film even it in the open air for about a week. Fullerene film display high stability and reproducibility during the electrochemical redox process.

### 3.4. Electrochemical studies

Cyclic voltammetric response to 1 mM potassium ferricyanide in 0.1 M  $\text{KNO}_3$  studied at different scan rates. Current slightly enhances in the case of modified electrode compared to bare carbon paste electrode when the film thickness maintained at 3 angstrom units (figure 2), but decreases if the thickness increases to 6 angstrom units, because highly organized densely packed  $\text{C}_{60}$  films rarely find electrochemical applications because counterions can hardly enter the film during electrochemical oxidation and reduction, thus precluding efficient charge exchange with the electrode substrate [12].

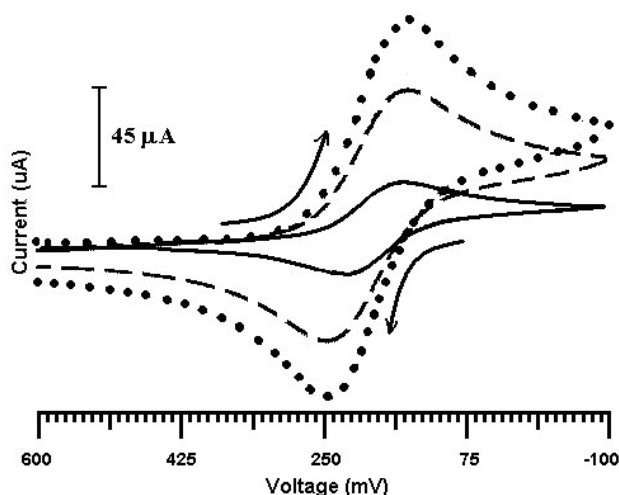

**Figure 2.** CVs of ferricyanide at bare CPE (solid line), at  $\text{C}_{60}/\text{CPE}$  (dotted line) where coating of  $\text{C}_{60} = 3 \text{ \AA}$  and at  $\text{C}_{60}/\text{CPE}$  (dashed line) where coating of  $\text{C}_{60} = 6 \text{ \AA}$ . Supp. electrolyte:  $\text{KNO}_3$ , scan rate:  $100 \text{ mV s}^{-1}$

Here the thickness of the  $\text{C}_{60}$  coating onto carbon paste electrode important role, 3 angstrom coating onto CPE is very much felicitating rate of electron transfer.

### 3.5. Determination of the surface area of the electrode


The surface area of the modified electrode was determined by using the 1 mM potassium ferricyanide system in 1 M  $\text{KNO}_3$  using the equation

$$i_p = 2.65 \times 10^5 n^{2/3} A D_0^{1/2} \nu^{1/2} C_0^*$$

where  $i_p$  is the peak current in amperes,  $A$  is the area of the electrode in  $\text{cm}^2$ ,  $C_0^*$  is the concentration of electro active species in mM,  $D_0$  is the diffusion coefficient in  $\text{cm}^2 \cdot \text{s}^{-1}$  and  $\nu$  is the sweep rate in  $\text{Vs}^{-1}$ . The surface area of the electrode was found to be  $0.039 \text{ cm}^2$ .

### 3.6. Voltammetry of dopamine at CPE and $C_{60}/\text{CPE}$ .


Figure 3 shows the electrochemical studies of dopamine were carried out at both CPE and  $C_{60}/\text{CPE}$  electrode using pH 6.5 phosphate buffer aqueous solutions. Reversible behavior observed for dopamine system at  $C_{60}/\text{CPE}$ , the difference in peak potential is 60 mV and current ratio is almost equal to unity. The current increases for the dopamine system at  $C_{60}/\text{CPE}$  compared to bare carbon paste electrode due to the rate of electron transfer is quite good at  $C_{60}/\text{CPE}$ .

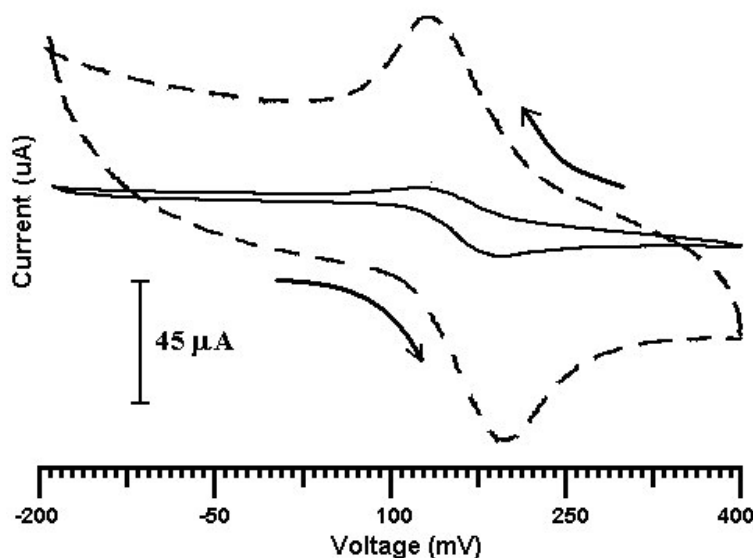


**Figure 3.** CVs of dopamine at bare CPE (solid line) and at  $C_{60}/\text{CPE}$  (dashed line) Supp. electrolyte:  $0.2 \text{ mol L}^{-1}$  phosphate buffer (pH 6.5); scan rate:  $100 \text{ mV s}^{-1}$

### 3.7. Electrochemical behavior of guanine and adenine

Modified electrode was practically used in this present work on the electrochemical response of adenine and guanine individually in  $0.2 \text{ mol L}^{-1}$  phosphate buffer (pH 7.2) solution. Figure.4a shows voltammogram of  $50 \text{ µmol L}^{-1}$  guanine at  $C_{60}/\text{CPE}$  which has a sensitive oxidation peak at  $0.77 \text{ V}$  in phosphate buffer pH 7.2. Figure. 4b shows the voltammogram of  $75 \text{ µmol L}^{-1}$  adenine at  $C_{60}/\text{CPE}$  which has a sensitive oxidation peak at  $0.98 \text{ V}$ . We examine the enhanced electrochemical response of adenine and guanine at  $C_{60}/\text{CPE}$  when compared to conventional electrode.

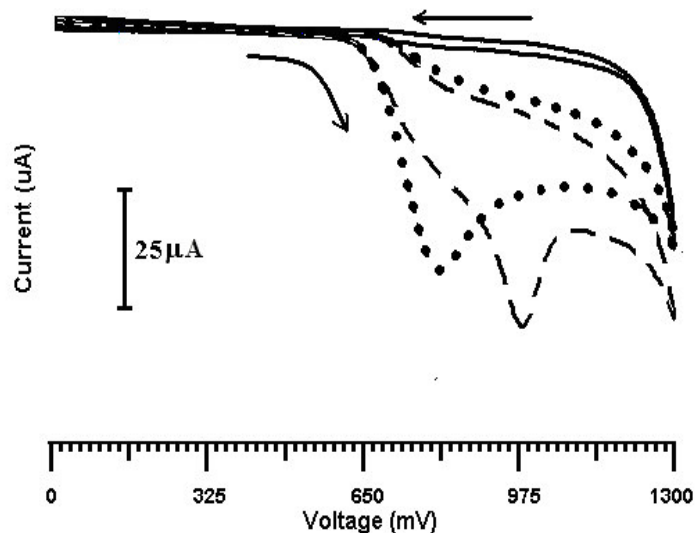

**Figure 4.** CVs of blank shown by solid line, dotted line represents  $50 \mu\text{mol L}^{-1}$  G and dashed line for  $75 \mu\text{mol L}^{-1}$  A at  $\text{C}_{60}/\text{CPE Supp.}$  electrolyte:  $0.2 \text{ mol L}^{-1}$  phosphate buffer (pH 7.2); scan rate:  $100 \text{ mV s}^{-1}$

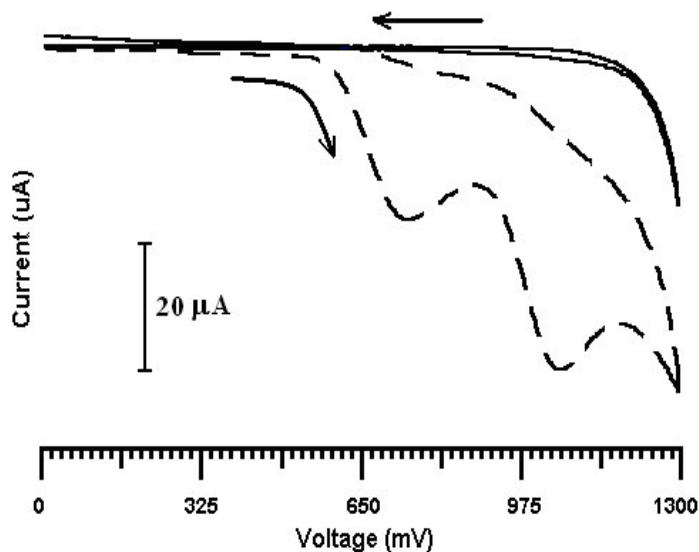


**Figure 5.** CVs of blank (solid line) and  $50 \mu\text{mol L}^{-1}$  G and  $75 \mu\text{mol L}^{-1}$  A (dashed line) at  $\text{C}_{60}/\text{CPE Supp.}$  electrolyte:  $0.2 \text{ mol L}^{-1}$  phosphate buffer (pH 7.2); scan rate:  $100 \text{ mV s}^{-1}$ .


### 3.8. Simultaneous determination of adenine and guanine

Figure 5 illustrated the CV response of  $50 \mu\text{mol L}^{-1}$  G and  $75 \mu\text{mol L}^{-1}$  A in  $0.2 \text{ mol L}^{-1}$  phosphate buffer (pH 7.2) solution on  $\text{C}_{60}/\text{CPE}$  and bare graphite electrode. It can be seen that, in the case of bare graphite electrode, the voltammograms of adenine and guanine exhibit just a small hump peak with the overlapping potential. Compared to the electrochemical response on bare electrode, in

the case of  $C_{60}/CPE$ , the peak current signals of adenine and guanine enhance significantly with their oxidative potential moving negatively, especially the oxidative potential of guanine moves negatively for about 300 mV which leads to the effective separation of the peak potentials of adenine and guanine. No cathodic peaks were observed on the reverse scan within the investigated potential range which indicated that adenine and guanine oxidation is an electrochemically irreversible process. The oxidation of guanine at solid electrode is expected to follow a two-step mechanism involving the total loss of four electrons and adenine occurs in three steps with total six electrons loss. In both cases, the first two-electron oxidation is rate-determining [15, 22 – 25].

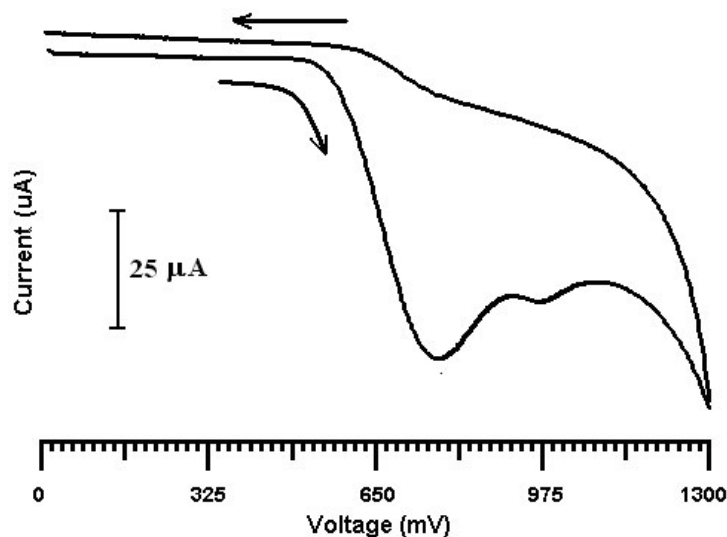

**Figure 6.** CV of  $75 \mu\text{mol L}^{-1}$  G and  $50 \mu\text{mol L}^{-1}$  A at  $C_{60}/CPE$  Supp. electrolyte:  $0.2 \text{ mol L}^{-1}$  phosphate buffer (pH 7.2); scan rate:  $100 \text{ mV s}^{-1}$ .

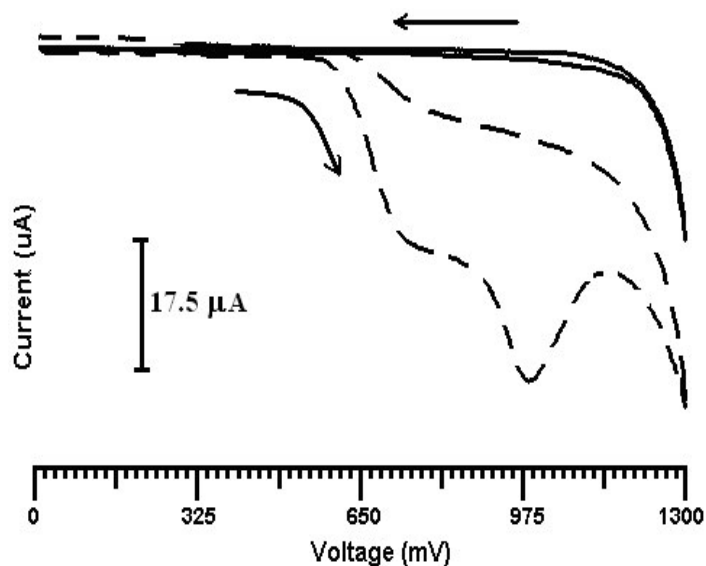

**Figure 7.** CVs of blank (solid line) and  $40 \mu\text{mol L}^{-1}$  G and  $75 \mu\text{mol L}^{-1}$  A (dashed line) at  $C_{60}/CPE$  Supp. electrolyte:  $0.2 \text{ mol L}^{-1}$  phosphate buffer (pH 7.2); scan rate:  $100 \text{ mV s}^{-1}$ .



We studied the reaction process at C<sub>60</sub>/CPE, by effect of scan rate to guanine electrochemical response. The CV of C<sub>60</sub>/CPE in the presence of 75 μmol L<sup>-1</sup> guanine in phosphate buffer is directly proportional to the scan rate over the range of 10–200 mV s<sup>-1</sup> further confirms that the guanine is absorbed on the surface of electrode. With increasing scan rate, the oxidation peak potential (E<sub>p</sub>) shifts to more positive values and there is a linear correlation between the peak potential and the logarithm of scan rate, log (v). These results indicate that the electrode process was controlled simultaneously by diffusion and adsorption. Figure 6 shows CV of 75 μmol L<sup>-1</sup> of guanine and 50 μmol L<sup>-1</sup> adenine at C<sub>60</sub>/CPE. Figure 7 shows CV of 75 μmol L<sup>-1</sup> of guanine and 50 μmol L<sup>-1</sup> adenine at C<sub>60</sub>/CPE A in 0.2 mol L<sup>-1</sup> phosphate buffer (pH 7.2),

#### 4. CONCLUSIONS

The present paper, demonstrates the electrochemical behavior of unmodified carbon paste surface and carbon paste modified by fullerene film. Fullerene film could be fabricated directly on the carbon paste surface by a simple physical vapor deposition process. Fullerene-modified CPE showed a high catalytic activity towards dopamine and potassium ferricyanide. Dopamine shows reversibility on C<sub>60</sub>/CPE. Various thickness of fullerene film can be fabricated on the CPE surface using the same protocol. Fullerene film display high stability during the electrochemical redox process. Adlayers prepared by sublimation in vacuum reveal better uniformity and fewer defects than original surface. This achievement has been demonstrated by scanning electron microscopy. The C<sub>60</sub>/CPE modified electrode can be successfully used to determine simultaneously adenine and guanine. Future efforts will aim at understanding better the structural-electrochemical reactivity of fullerene-modified electrodes and the factors that govern the electron-transfer kinetics of these attractive devices.

#### References

1. H. W. Kroto, J. R. Heath, S. C. O'Brien, R. F. Curl, R. E. Smalley, *Nature* [London], 318 (1985) 162
2. W. Kratschmer, L.D. Lamb, K. Fostiropoulos, D.R. Huffman, *Nature* [London], 347 (1990) 354
3. R. E. Haufler, J. Conceicao, L.P.E. Chibante, Y. Chai, N.E. Byrne, S. Flanagan, M.M. Haley, S. C. O'Brien, C. Pan, Z. Xiao, W. E. Billups, M.A. Ciufolini, R.H. Hauge, J.L. Margrave, L.J. Wilson, R.F. Curl, R.E. Smalley, *J. Phys. Chem*, 94 (1990) 8634.
4. L. Echegoyen, F. Diederich, L.E. Echegoyen, *Fullerenes: Chemistry, Physics, and Technology*, Eds K.M. Kadish, and R.S. Ruoff, John Wiley and Sons New York. (2000)
5. B.S. Sherigara, W. Kutner, F. D'Souza, *Electroanalysis*, 15 (2003) 753.
6. Francis D'Souza, Lisa M Rogers., Erin S O'Dell, Agnieszka Kochman, Wlodzimierz Kutner., *Bioelectrochemistry*, 66 (2005) 35.
7. H.W. Kroto, J.E. Fischer, D.E. Cox, Eds. *Fullerenes*; Pergamon Press: Oxford, U.K. (1993)
8. K. Tomura, M. Nishizawa, D. Takemura, T. Matsue, L. Uchida, *Chem. Lett.*, (1994) 1365.
9. J.J. Carlisle, C.A. Wijayawardhana, T.A. Evans, P.R. Melaragno, I.B. Ailin-Pyzik, *J. Phys. Chem*, 100 (1996) 1532

10. P. Janda, T. Krieg, L. Dunsch, *Adv. Mater.*, 10 (1998) 1434
11. J.A. Leiro, M.H. Heinonen, T. Laiho, I.G. Batirev, *J. Electron Spectrosc. Relat. Phenom.*, 128 (2003) 205
12. Lobo R F and Silva N T *Rev. Sci. Instrum.*, 72 (2001) 3505
13. J. Chlistunoff, D. Cliffl, and A. J. Bard, Electrochemistry of fullerene films, *Thin Solid Films.*, 257 (1995)166
14. Wlodzimierz Kutner, Piotr Pieta, Robert Nowakowski, Janusz W. Sobczak, Zbigniew Kaszukur, Amy Lea McCarty, Francis D'Souza, *Chem. Mater.*, 17 (2005) 5635
15. H.S. Wang, H.X. Ju, H.Y. Chen, *Anal. Chim. Acta* 461 (2002) 243
16. J.M. Zen, M.R. Chang, G. Ilangovan, *Analyst* 124 (1999) 679.
17. T.A. Ivandini, B.V. Sarada, T.N. Rao, A. Fujishima, *Analyst* 128 (2003) 924.
18. A. Abbaspour, M.A. Mehrgardi, R. Kia, *J. Electroanal. Chem.* 568 (2004) 261.
19. Zonghua Wang, Sufang Xiao, Yue Chen, *J. Electroanal. Chem* 589 (2006) 237
20. Q. Zhu, D.E. Cox, J.E. Fischer, K. Kniaz, A.R. McGhie and O. Zhou, *Nature*, 355 (1992) 712.
21. W. Kratschmer, L.D. Lamb, K. Fostiropoulos and D.R. Huffman, *Nature.*, 347 (1990) 354
22. B.M.A. Christopher, B.M.O. Ana, S.H.P. Serrano, *J. Electroanal. Chem.* 366 (1994) 225.
23. A.M. Oliveira-Brett, J.A.P. Piedade, S.H.P. Serrano, *Electroanalysis* 12 (2000) 969.
24. G. Druyhurst, *J. Electrochem. Soc.* 116 (1969) 1411.
25. G. Druyhurst, P.J. Elving, *J. Electrochem. Soc.* 115 (1968) 1014